

To Oscar Monning
with the compliments of the writers

The Breece, New Mexico, meteoritic iron

BY

CARL W. BECK, Ph.D., LINCOLN LAPAZ, Ph.D.,
and LOUIS H. GOLDSMITH, M.S.

THE UNIVERSITY OF NEW MEXICO, ALBUQUERQUE, NEW MEXICO, U.S.A.

[Reprinted from the *Mineralogical Magazine*, London, March 1951,
Vol. XXIX, No. 212, pp. 531-537.]

MINERALOGICAL SOCIETY

Officers and Council for 1950-51

PRESIDENT

Prof. C. E. TILLEY, B.Sc., Ph.D., F.R.S.

PAST-PRESIDENTS

L. J. SPENCER, C.B.E., B.Sc., M.A., Sc.D., F.R.S. (1936-39).	Lt.-Col. W. CAMPBELL SMITH, C.B.E., M.C., T.D., M.A., Sc.D., F.G.S. (1945-48).
Sir ARTHUR RUSSELL, Bart., M.B.E. (1939-42).	

VICE-PRESIDENTS

A. F. HALLIMOND, M.A., Sc.D., F.G.S.	S. J. SHAND, D.Sc., Ph.D., F.G.S.
---	-----------------------------------

TREASURER

E. H. BEARD, B.Sc.

*Mineral Resources Division, Imperial Institute, South Kensington,
London, S.W. 7*

GENERAL SECRETARY

G. F. CLARINGBULL, B.Sc., Ph.D., F.G.S.

British Museum (Natural History), Cromwell Road, London, S.W. 7

FOREIGN SECRETARY

L. J. SPENCER, C.B.E., B.Sc., M.A., Sc.D., F.R.S.

EDITOR OF THE JOURNAL

L. J. SPENCER, C.B.E., B.Sc., M.A., Sc.D., F.R.S.

111 Albert Bridge Road, London, S.W. 11

MANAGING TRUSTEES

Prof. C. E. TILLEY, B.Sc., Ph.D., F.R.S.	Lt.-Col. W. CAMPBELL SMITH, C.B.E., M.C., T.D., M.A., Sc.D., F.G.S.
---	---

ORDINARY MEMBERS OF COUNCIL

S. O. AGRELL, B.A., Ph.D., F.G.S.	H. M. POWELL, M.A., B.Sc.
F. A. BANNISTER, M.A., Sc.D., F.Inst.P.	H. P. ROOKSBY, B.Sc., F.Inst.P.
H. G. DINES, A.R.S.M., F.G.S.	P. A. SABINE, A.R.C.S., F.G.S.
G. S. GOWING, M.A., F.G.S.	F. H. STEWART, B.Sc., Ph.D., F.G.S.
G. E. HOWLING, B.Sc.	S. I. TOMKEIEFF, M.Sc., D.Sc., F.G.S.
J. PHEMISTER, M.A., D.Sc., F.R.S.E., F.G.S.	A. K. WELLS, D.Sc., F.G.S.

CLAY MINERALS GROUP

*Chairman: Prof. A. L. ROBERTS, Ph.D.
Fuel Dept., The University, Leeds, 2*

*Hon. Secretary: R. C. MACKENZIE, B.Sc., Ph.D.
Macaulay Institute for Soil Research,
Craigiebuckler, Aberdeen*

*Bankers and Custodian Trustee.—Messrs. Coutts & Co., 15 Lombard
Street, London, E.C. 3*

The Breece, New Mexico, meteoritic iron.

By CARL W. BECK, Ph.D., LINCOLN LAPAZ, Ph.D., and LOUIS H. GOLDSMITH, M.S.

The University of New Mexico, Albuquerque, New Mexico, U.S.A.

[Read November 11, 1950.]

Introduction.

THE literature of meteoritics contains little information about the unusual Breece meteorite. This iron appears to be mentioned only in museum accession reports and catalogues of meteorite collections,¹ and the sole information supplied by these references consists of the approximate date of find (1921), the approximate weight (50 to 51 kg.), the approximate place of discovery, near Breece, McKinley County, New Mexico, in latitude 35° 18' N., longitude 108° 18' W., and the classification (Om). At the time of the discovery the hamlet of Breece² was the centre of a small lumbering industry, since moved SW. and SE. into more heavily forested areas, and today it has few inhabitants. The find consisted of a single well-preserved mass which was purchased in its entirety from an unnamed source by the Field Museum of Chicago approximately ten years after the iron was discovered.

The Heaston Collection of New Mexico meteorites at the University of New Mexico contains an interesting end-piece (fig. 1) weighing 920 grams sawn from the single mass which comprises the Breece find. The maximum dimensions of this specimen in three directions at right angles are 14.5 × 7.1 × 2.3 cm. This end-piece, registration number IOM-11 in the Institute of Meteoritics, the University of New Mexico, is the

¹ Ann. Rep. Field Mus. Nat. Hist. Chicago, 1932, for 1931, vol. 9, p. 133. H. H. Nininger, *Our stone-pelted planet*, Boston and New York, 1933, p. 158; *The Nininger collection of meteorites*. Mines Mag. Colorado School of Mines, 1933, vol. 23, pp. 6-9, 12 (p. 2 of reprint, 747 grams). [M.A. 5-400, 405.] M. H. Hey, *Second appendix to the catalogue of meteorites . . . British Museum*. London, 1940, p. 24. [M.A. 7-534.] A. L. Coulson, *A catalogue of meteorites . . . Indian Museum*. Mem. Geol. Surv. India, 1940, vol. 75, p. 57. [M.A. 8-54.] S. A. Northrop, *Minerals of New Mexico*. Bull. Univ. New Mexico, 1942, no. 379 (Geol. Ser., vol. 6, no. 1), p. 186. [M.A. 8-357, 9-131.] S. H. Perry, *The metallography of meteoric iron*. Bull. U.S. Nat. Mus., 1944, no. 184, p. 167, pl. 47. [M.A. 9-290.] F. C. Leonard, *A catalog of provisional coordinate numbers for the meteoritic falls of the world*. Univ. New Mexico Publ. Meteoritics, 1946, no. 1, p. 41. [M.A. 10-171.] S. H. Perry, *Meteorite collection of Stuart H. Perry . . . 1947*, p. 3 (1487 grams, donated to University of Michigan).

² Breece is shown in the U.S. Geol. Surv. Topographic map of the state of New Mexico, edition of 1925, and on the U.S. Geological map of New Mexico, by N. H. Darton, edition of 1928; both maps 1 : 500,000.

subject of the mineralogical and chemical investigations reported in the present paper. This specimen, with its hackly fracture, presents evidence that the original 51-kg. mass was only a fragment of a larger mass which disrupted during transit through the atmosphere. Because of this

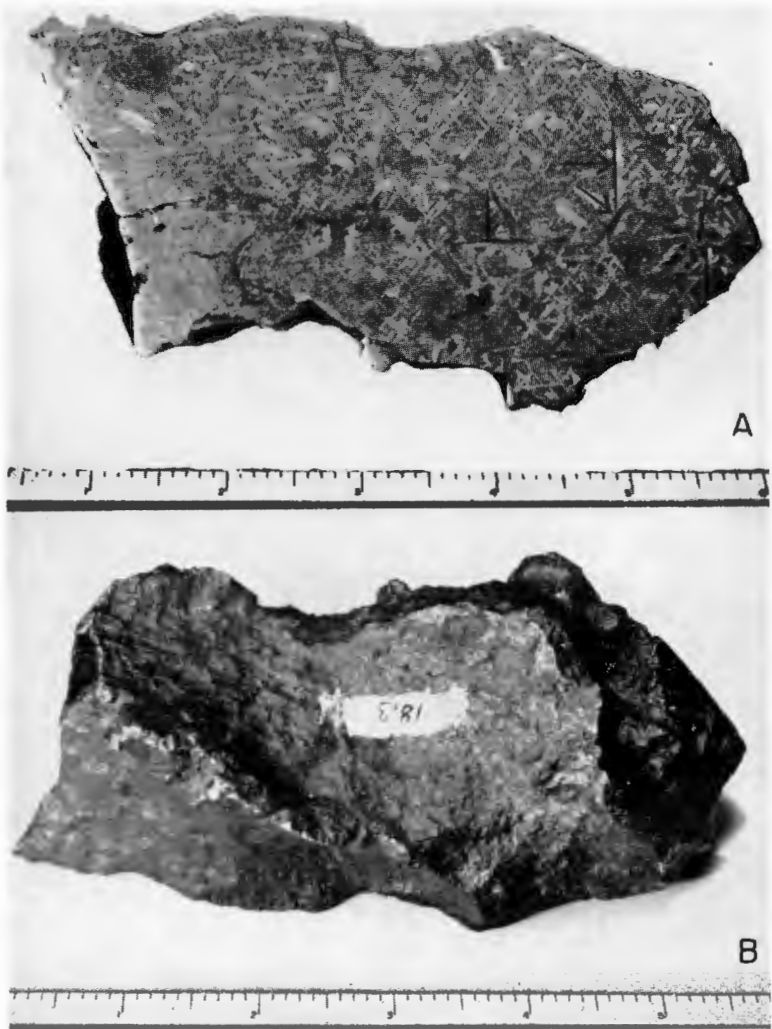


FIG. 1. Breece, New Mexico, siderite. A. Macro-etched surface; arrows point to cohenite lamellae. B. Exterior surface. $\times \frac{2}{3}$ (scale of inches).

evidence, an effort has been made to discover additional masses of the fall. Information supplied by Mr. Herbert Dick and Mr. L. E. Roderick of Albuquerque, New Mexico, and in particular by Mr. Charles Allen, a mineral collector of Trinidad, Colorado, leads to the apparently well-substantiated existence of a second fragment of the meteorite found in 1941 at one of the logging camps near Breece. Several searches with drag magnets and meteorite detectors have been made in the areas designated by these informants, but no additional finds were made. At the moment it must be presumed that the 51-kg. mass sold to the Field Museum constitutes the only fragment recovered and recognized from this fall.

Macroscopic examination.

The external crustal surface of the Breece meteorite (fig. 1B) is typical of most iron meteorites. The colour is dark brown to black, and the surface exhibits ample evidence of piezoglyphs, pressure markings produced during flight through the earth's atmosphere. The crustal coating ranges from vanishingly thin to a maximum thickness of 0.5 mm. The oxidation of the meteorite is limited to the surface and along cracks which penetrate into the interior of the iron (fig. 1A). Otherwise the meteorite is exceedingly well preserved; and, from this observation, it may be assumed that the fall did not antedate the find by many years.

The sawn surface of the meteorite was polished and macro-etched (fig. 1A). The metallographic structure is revealed to be that of an octahedrite. Lamellae of kamacite range in thickness from 0.6 to 1.2 mm., although some short lamellae have local thicknesses up to 1.8 mm. Because the greatest proportion of kamacite bands falls in the range of 0.6–1.0 mm., the Breece meteorite is classified in the division of siderites (Si), class octahedrites (O), subclass medium octahedrite (Om). The kamacite bands are in three systems forming good equilateral triangles; apparently the cut was made parallel to an octahedron plane. The kamacite bands are bordered by taenite lamellae which are, for the most part, much thinner than the kamacite. The angular interstices are filled with plessite fields, which, macroscopically, are triangular in form.

Another type of lamellae appears prominently in the macro-etch (fig. 1A, arrows). These lamellae are finely developed and either parallel to or perpendicular to kamacite bands. They average about 0.8 mm. in thickness and attain a maximum length of 1.8 cm. These lamellae in the Breece meteorite were noted by Perry (loc. cit., 1944) and referred to by him as Reichenbach lamellae. He says (p. 17): 'In octahedral irons

troilite is occasionally observed in the form of scattered plates or lamellae with a definite cubic orientation unrelated to the octahedral pattern.' Farrington says the Reichenbach lamellae form 'parallel to the faces of a cube or dodecahedron' (p. 100),¹ but contradicts this later (pp. 143, 150) by saying they form parallel to the cube. A similar arrangement of schreibersite parallel to planes of the dodecahedron is referred to by Farrington (pp. 100, 150) as the Brezina lamellae of Cohen. Dr. L. J. Spencer (personal communication), has pointed out that in the rhombic dodecahedron orientation traces of (110), (101), (011) and their opposite faces are parallel to octahedral edges, and traces of ($\bar{1}\bar{1}0$), ($\bar{1}01$), ($0\bar{1}1$) and their opposite faces are perpendicular to octahedral edges on the face (111), while cube traces are all parallel to octahedral edges. Inasmuch as these lamellae in the Breece meteorite are both parallel and perpendicular to the octahedral edges, they are presumed to be parallel to the rhombic dodecahedron. The lamellae figured by Perry (pl. 47), on a section of Breece approximately parallel to (111), are also parallel and perpendicular to octahedral edges; but when referring to them as Reichenbach lamellae (p. 167) no mention is made of either troilite or cohenite.

Several of these lamellae were isolated and subjected to three separate qualitative chemical analyses. In all three cases abundant carbon was obtained, and sulphur was completely absent. In two of these analyses phosphorus was absent, while the third showed a trace. The complete chemical analysis of the Breece siderite (table I) also shows phosphorus to be absent and confirms the presence of carbon, though the small amount of carbon would indicate that the analysed fragment contained at best but a small lamella. These analyses suggested that the lamellae are composed of cohenite. A quantitative analysis of another cohenite lamella is shown in table II. The results remove any possible doubts as to the nature of these lamellae. These same lamellae were observed in the microscopic examination of small polished sections. Immersion for 90 seconds in boiling alkaline sodium picrate, prepared by dissolving 12.5 g. of sodium hydroxide in 50 c.c. of water and adding 2 g. of picric acid, darkened the lamellae and confirmed that they are cohenite.

Cohenite is conventionally regarded as a rare meteoritical mineral. It has been reported from the Magura, Bendegó, Wichita County, Beaconsfield, Canyon Diablo, Cosby's Creek, and several other iron meteorites (Perry, loc. cit., 1944, p. 22). In physical appearance

¹ O. C. Farrington, *Meteorites, their structure, composition, and terrestrial relations*. Chicago, 1915.

cohenite is identical with schreibersite, and distinguished from it with difficulty. The above test with boiling alkaline sodium picrate is the most diagnostic test for cohenite. In truth, it is to be expected that a more universal application of this etch test to polished sections would reveal that cohenite is more common than it is now believed to be.

The absence of sulphur in the lamellae makes the designation of Reichenbach lamellae inapplicable to this structure, and, as the presence of schreibersite appears doubtful at best, the term Brezina lamellae is equally inapplicable. These lamellae are similar physically to both the Reichenbach and Brezina lamellae, but the comparisons must be confined to structural relations only.

Microscopic examination.

Two slices of the Breece, New Mexico, siderite were mounted in bakelite, polished, etched with nital for 15 seconds, and studied with the metallographic microscope.

The microscope study shows that the external zone of alteration is extremely small, and that the interior of the meteorite, except along fractures, is free from alteration. From the unaltered appearance of the kamacite, taenite, and plessite, it may be assumed that the interior of the meteorite did not become appreciably heated during the flight through the atmosphere. Heating and the resultant fusion crust were confined to a thin outer zone.

The meteoritical components present are kamacite, taenite, plessite, cohenite, and troilite. The principal constituent is kamacite, the alpha nickel-iron alloy. In the macro-etched specimen the kamacite displays a characteristic sheen which changes as the surface is rotated. On the well-polished sections the kamacite is tin-white and occurs either as narrow, tapering lamellae bounded by very fine, fairly regular taenite and usually in a field of dense plessite (fig. 2); or it occurs as broad plates of two types: (1) apparently structureless, and (2) granular. Some of the latter type of kamacite show several sets of well-developed Neumann lines. Because Neumann lines can be obliterated in the laboratory upon heating, their presence is further confirmation that the siderite did not become heated in the interior.

Taenite, the gamma nickel-iron alloy, occurs usually as fine, fairly continuous bands bounding the kamacite lamellae (fig. 2) and forming the distinctive Widmanstetter pattern. Taenite also occurs as highly irregular patches. These patches range in appearance from entirely taenite, through taenite with some interior plessite (the 'fleckig' or

'spotted' taenite), to dense plessite with a border of taenite, the result of an incomplete separation of kamacite and taenite. In these taenite-plessite patches the plessite becomes increasingly denser towards the centre of the patch.

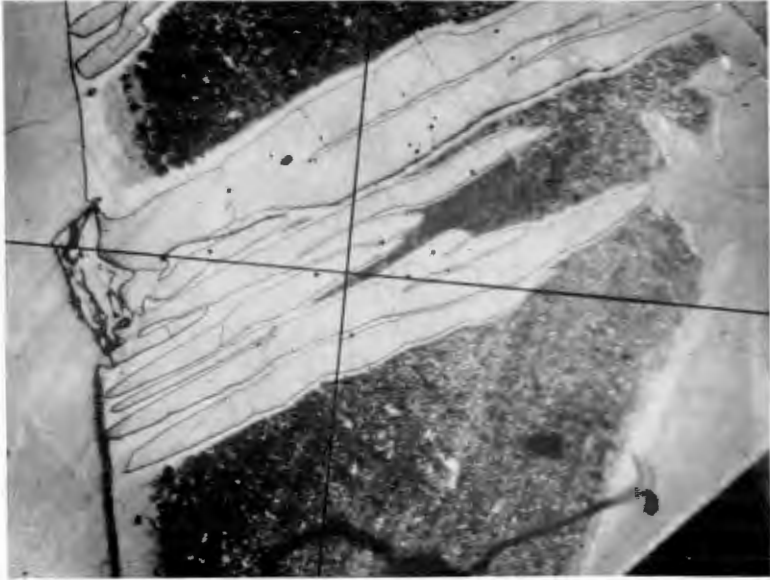


FIG. 2. Breece, New Mexico, siderite. Kamacite lamellae bounded by narrow taenite and surrounded by dense plessite. An irregular grain of brittle cohenite shows near the left-hand edge of the photomicrograph. $\times 125$.

Most of the plessite on the polished sections is of the dense variety. Under high magnification the dense plessite can be seen to be composed of minute taenite particles embedded in a mesostasis of kamacite. These fields occupy the spaces formed by the lamellae of kamacite and taenite in octahedral arrangement.

In the polished sections cohenite generally appears as narrow, tin-white, brittle bands concentrated along the boundaries of contiguous kamacite plates, but occasionally an irregular grain of cohenite can be seen (fig. 2). That these are cohenite, and not schreibersite, was confirmed again by the boiling alkaline sodium picrate test.

Troilite occurs as tiny, irregular grains associated with the kamacite plates. In the Breece meteorite the troilite is typically brownish in colour.

Chemical analyses.

A portion of the Breece meteorite was removed from the mass, etched, and studied with a microscope to be certain it was representative of the meteorite. A chemical analysis was made by Dr. E. L. Martin, Department of Chemistry, the University of New Mexico, and the results are shown in table I. The analysis is in agreement with that of a normal medium octahedrite, though possibly a little higher in nickel than usual.

An analysis of one of the cohenite lamellae was made by Carl W. Beck. The results are shown in table II, and are consistent with the formula R_3C for cohenite where R = iron, nickel, and cobalt.

TABLE I. Chemical analysis made on 1.743 grams of the Breece siderite.

			%			
Fe	89.87	Specific gravity	...	7.93
Ni	9.26	Molecular ratio $\frac{Fe}{Ni}$...	10.20
Co	0.89			
S	0.11	Molecular ratio $\frac{Fe}{Ni+Co}$		9.34
C	0.03			
P	0.00			
Cl	0.00			
Cu	0.00			
			100.16			

TABLE II. Chemical analysis made on 0.4764 gram of cohenite.

			%	Molecular ratios.	
Fe	91.35	1.6356	}
Ni	1.64	0.0279	
Co	0.11	0.0019	
C	6.54	0.5450	1.000
			99.64		
Specific gravity	7.37		

Summary.—The investigation of the Breece, New Mexico, siderite shows it to be a medium octahedrite (Om) composed chiefly of kamacite with lesser amounts of taenite bands and plessite fields. The most interesting constituent is cohenite as well-defined lamellae in the unusual arrangement similar to the familiar Reichenbach and Brezina lamellae.

MINERALOGICAL SOCIETY PUBLICATIONS

The Publisher is Geoffrey Cumberlege, Oxford University Press, *Amen House, Warwick Square, London, E.C. 4.*

Mineralogical Magazine.—Current Numbers price 12s. net each. Annual Subscription for four Numbers post free 40s., payable in advance to the Publisher, either direct or through any bookseller. Since 1920 (No. 88, Vol. XIX) the numbers have been issued quarterly, and include a separately-paged appendix of *Mineralogical Abstracts*.

Back Numbers.—The following numbers are out of print: 17–23, 73, 75, 77–9, 89, 90–5, 98–9, and 121–2. Moreover, certain numbers, the stock of which is low, are reserved for purchasers of part sets of the Magazine, and can only be sold as part of such sets. With the above exceptions, all numbers can be supplied at the following rates: Nos. 1–87 (Vols. I–XVIII, 1876–1919), No. 12* (Geological Map of the Shetland Islands, mounted and folded, which was issued as an addition to Vol. II), and the General Indexes to Vols. I–X and XI–XX, price 5s. each net. (To Members less 20% discount.) Nos. 88 onwards (Vols. XIX onwards, 1920–) at 12s. each net, or 40s. per annual issue of four numbers.

Mineralogical Abstracts (Vol. I, Nos. 1–12, 1920–22, issued with Vol. XIX of the Magazine) are also sold separately. Price 5s. net each number. Later numbers are issued only as part of the Magazine.

Bye-Laws and List of Members (1950). Price 2s. 6d. net.

Inquiries from Members of the Society concerning publications should be addressed to the General Secretary and not to the Publisher.

GENERAL NOTICES

Candidates for Election as Ordinary Members should obtain a nomination form from the General Secretary, Dr. G. F. Claringbull, *British Museum (Natural History), Cromwell Road, London, S.W. 7.* Candidates must be proposed by two Members of the Society, one, at least, of whom shall have personal knowledge of the candidate. There is an entrance fee of one guinea and the annual subscription is one guinea; the latter can be compounded for by a single payment of thirty pounds (£30). New Members, on the payment of their first subscription, receive all the numbers of the Magazine for the year for which the subscription is paid.

There are at least four meetings of the Society each year, on Thursdays, in January, March, June, and November. They are held (by kind permission) in the Apartments of the Geological Society, Burlington House, Piccadilly, London, W. 1. Titles of papers to be read at these meetings, with a view to subsequent publication in the Magazine, and of exhibits, should be sent with a short abstract to the General Secretary at least *three* weeks before the meeting. Authors alone are responsible for the views set forth in their respective papers. They are allowed, free of charge, fifty separate copies of their papers published in the Magazine.

MINERALOGICAL MAGAZINE

CONTENTS OF No. 212

(March 1951)

F. H. STEWART: The petrology of the evaporites of the Eskdale, no. 2 boring, east Yorkshire. Part II. The middle evaporite bed. (With Plates IX and X)	445
G. R. MCLACHLAN: The aegirine-granulites of Glen Lui, Braemar, Aberdeenshire. (With Plate XI)	476
K. NORRISH: Priderite, a new mineral from the leucite-lamproites of the west Kimberley area, Western Australia	496
G. W. BRINDLEY: The crystal structure of some chamosite minerals. Appendix: Geological and petrographical notes by K. C. DUNHAM, V. A. EYLES, and J. H. TAYLOR. (With Plate XII)	502
H. G. MIDGLEY: A serpentine mineral from Kennack Cove, Lizard, Cornwall	526
C. W. BECK, L. LAPAZ, and L. H. GOLDSMITH: The Breece, New Mexico, meteoritic iron	531
F. L. STILLWELL and A. B. EDWARDS: Jacobsite from the Tamworth district of New South Wales	538
W. T. HARRY: On a cupriferous Lewisian para-gneiss	542

MINERALOGICAL ABSTRACTS

(Vol. 11, No. 4, pp. 181-252)

Notices of Books (p. 181).—New Minerals (p. 186).—Artificial Minerals (p. 191).—Rock-forming Minerals and Petrology (p. 199).—Economic Minerals and Ore-deposits (p. 210).—Clay Minerals (p. 216).—Radioactivity and Uranium Minerals (p. 224).—X-rays and Crystal Structure (p. 232).—Miscellaneous (p. 243).

Authors of papers abstracted.—Adams, 235, Agrawal 203, Ahrens 224, 226, Alberman 228, Alcock 239, Anderson 228, Arnott 228, Backström 206, Bacon 235, Bairsto 233, Barrer 194, Barshad 218, 221, Bárta 207, 222, Bassett 193, Bateman 184, Bates 221, Beard 189, Beck 216, Berdesinski 192, Berg 185, Berry 240, Bertolani 249, Bertrand 245, Beus 190, Bhatnagar 204, Biljon 204, Blumenthal 215, Borland 218, Bracewell 251, Brasseur 194, Brenet 238, Brooks 239, Buerger 232-4, Burri, 181, Byström 237-8, Caillere 190, 210, 220, Čáp 222, Carobbi 193, Cavalca 239, Chaudron 193, Chayes 203, Chenevoy 207, Chudoba 201, Chukhrov 247, Church 225, Cisney 189, Clausen 252, Cole 233, Conybeare 228, Coombs 203, Coppens 224, Correns 208, Cotelto Neiva 211, Dake 224, Dallemagne 194, Danielsson 208, Delavault 210, De Ment 224, Denayer 209, Denysshchen 222, Dreyer 202, Dyal 217, Earley 236, Eaton 191, Elgabaly 218, Ernst 198, Escard 219, Esquevin 220, Evans 224, 229, 230, Fahey 243-4, Fenner 204, Ferguson 228, Ferrari 239, Fersman 184, Fischer 227, Fleck 215, Fornasari 241, Frechen 201, Foster 197, 243, Frondel 187 229, 230, Friedensburg 185, Fruer 236, Fumano' 250, Galloni 188, Garrela 202, Gentner 224, Ginzburg 189, Göksu 215, Gorfinkle 226, Grasselly 214, Green 212, Grigoriev 195, Hartshorne 181, Hayton 251, Hedlik 237, 241, Heinrich 213, Hellmers 209, Hellner 242, Hendricks 217, Hénin 190, 210, 220 Hildebrand 221, Hinds 194, Holland 225, Howland 202, Hummel 196, Hurlbut 230, Hurley 226, Hutchinson 245, Hutton 209, Hyde 191, Ito 232, 242, Jaffe 245, Jeffery 233, Kawano 202, Keevil 227, Keller 231, Kelley 211, Kendall 191, 196, Kerr 216, Kiefer 249, King 212, Kiriyaama 241, Koblitz 246, Koch 250, Kokkoros 240, Köppen 196, Koutek 210, Krishnamoorthy 217, Kristoffersen 191, Kulp 225, Kuno 204, Kunsy 246, Kurylenko 252, Kutina 190, Lanoman 252, Leitmeier 183, Lerner 252, Levin 201, Lindberg 187, Lokka 202, 226, Lombaard 205, McAndrew 186, McConnell 220, M'Erwen 220, Machatschki 240, McKelvey 227, McLachlan 205, Magéli 239, Mahadevan 206, Marble 231, Marel 216, Mason 188, Mathieu-Sicaud 190, Matthes 207, 216, Mazurak 217, Mehnert 213, Mélon 194, Mering 219, Mezősi 214, Michel-Lévy 195, Millman 210, Milton 245, Minguzzi 249, Misra 204, Morgan 196, Morgante 214, Mori 240, Morimoto 235, Mould 220, Mrose 229, Muench 226, Müllenburg 231, Murdoch 243, Muthuswami 231, Myers 245, Nelson 227, Norrish 243, Novotny 199, Nuffield 244, O'Daniel 242, Orel 210, Osborn 198, Overholt 245, Overstreet 217, Pabst 188, 237, Page 227, Paghiani 250, Pákozdy 250, Pauly 201, Peacock 186, Pecora 244, Pernoux 248, Perrin-Bonnet 219, Phoenix 244, Picard 191, Poldervaart 206, Pulfrey 206, Radhakrishna 215, 223, Radic 247, Ramdohr 187, Rankama 251, Reiche 208, Reitemeier 218, Robertson 234, Rodda 245, Roeber 200, Rojas-Cruz 218, Rood 191, Rooksby 239, Rosenqvist 231, Sabatier 195, 248-9, Sajanaga 242, Saito 211, Sakamoto 211, Sakurai 241, Salmon 194, Sander 183, Sandrea 225, 252, Satava 222, Sathapathi 206, Schairer 198, Schaller 187, Schlossmacher 186, Schröder 192, Scüller 185, Schumann 182, 209, Scott 191, Seeliger 213, Sgroso 214, Shamin 225, Sharma 203-4, Sharp 233, Sherwood 189, Shirozo 212, Silva 214, Smits 224, Sommerlatte 185, Spraggon 196, Srinivasan 232, Stringham 223, Strunz 189, Stuart 181, Swineford 221, Takuchi 242-3, Taneda 200, Teichner 248, Terrey 194, Tertian 237, Tombs 239, Tunell 235, Tyndale-Biscoe 205, Ueda 240, Vachtl 207, Van Tassel 246, Vašiček 207, Vaux 245, Ventriglia 216, Vitallano 188, Wadley 192, Wallaays 193, Warde 222, Warren 210, Wasserstein 235, Watanabe 242, Watt 193, Webb 210, Weeks 189, Weisz 233, White 224, Wiklander 218, Wilhelm 237, Williams 233, Wood 233, Wright 182, Wyckoff 191, Yagoda 224, Yarzhenyky 247, Yeo 191, Yoder 197, Zemann 234-5.